

Magnetic Excitation in Artificially Designed Oxygen Molecule Magnet

Takatsugu MASUDA*, Satoshi TAKAMIZAWA, Kazuma HIROTA¹, Masaaki OHBA², and Susumu KITAGAWA²

International Graduate Schools of Arts and Sciences Yokohama City University, Yokohama, 236-0027

¹*Institute of Solid State Physics, the University of Tokyo, Kashiwa, 277-8581*

²*Department of Synthetic Chemistry and Biological Chemistry, Kyoto University, Kyoto, 615-8510*

We performed inelastic neutron scattering experiment to study magnetic excitation of O₂ molecules adsorbed in microporous compound. The dispersionless excitation with characteristic intensity modulation is observed at $\hbar\omega = 7.8$ meV at low temperature. The neutron cross section is explained by spin dimer model with intradimer distance of 3.1 Å. Anomalous behaviour in the temperature dependence is discussed in the context of enhanced magnetoelasticity in the soft framework of O₂ molecule.

KEYWORDS: Oxygen molecule, spin dimer, neutron scattering

Oxygen molecule, the second most abundant constituent in air, is essential to human beings. One of the interesting physical properties is that the diatomic molecule has magnetism with effective spin of $S = 1$. In solid state at low temperature the oxygen behaves as insulating low-dimensional antiferromagnets¹ through exchange interaction induced by the significant overlap of the molecular orbital. Under pressure the change of electronic structure brings exotic phenomena such as metallization,² superconductivity³ and exotic magnetic orders.^{4,5} Now the understanding of magnetic oxygen as an elementary substance has been progressed. The next challenge is to design a magnet by treating oxygen molecule as a magnetic entity. Enterprising trial for the O₂ based magnet was performed in adsorbing O₂ monolayer on graphite substrate.^{6,7} Neutron diffraction and magnetic susceptibility study revealed the structural and magnetic variation of the artificially designed triangular lattice of O₂ molecule with the change of the oxygen density and temperature. However the amount of the oxygen in the monolayer is too small to be detected for a dynamical probe such as neutron inelastic scattering technique. For further magnetic study availability of bulk size magnet has been required.

One solution is to utilize microporous compounds in a recently developing chemistry area, coordination polymers science.^{8–10} Particularly interesting is a copper coordination polymer $\{[\text{Cu}_2(\text{pyrazine-2,3-dicarboxylate})_2(\text{pyz})]2\text{H}_2\text{O}\}_n$ abbreviated as CPL-1.¹¹ Molecule formula is C₁₆H₁₂Cu₂N₆O₁₀. The space group is monoclinic $P2_1/c$ and the lattice constants are $a = 4.693$ Å, $b = 19.849$ Å, $c = 11.096$ Å, and $\beta = 96.90^\circ$. The compound includes 1D channel for physical adsorption of molecules with the dimension of 4.0 Å by 6.0 Å in crystallographic a direction (Fig. 1(a)). A strong confinement effect due to the restricted bore size enables the formation of ladder-like array of adsorbed oxygen¹² through van der Waals interaction. The intermolecular distance in the rung/dimer direction is 3.28(4) Å. Unlike the surface adsorption on graphite O₂ molecules penetrate inside and the amount of the adsorption is one molecule

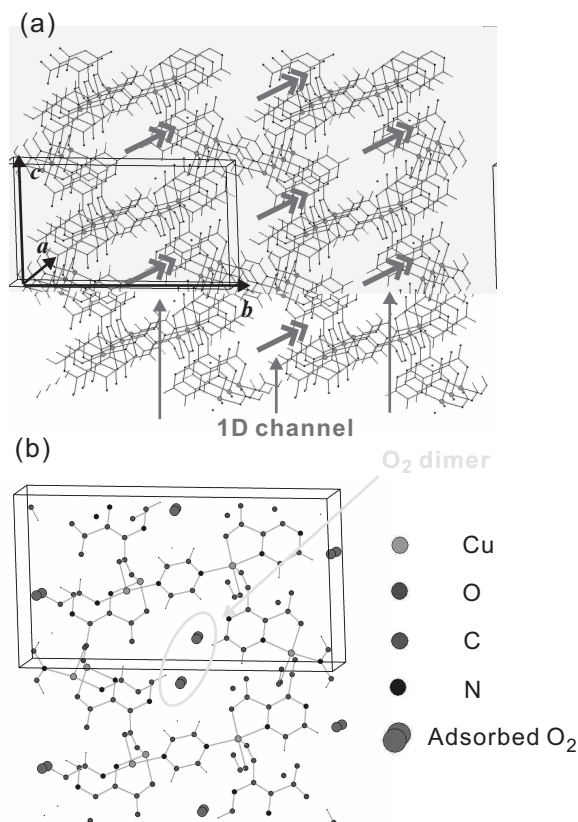


Fig. 1. (Color online) Crystal structure of the microporous copper coordination polymer (CPL-1). (a) The framework of non-adsorbed CPL-1. 1D channel for molecules adsorption runs in crystallographic a direction. (b) Structure of CPL-1 with O₂ adsorption.

per one copper atom. Hence the O₂ based magnet of bulk size is realized. The magnetic susceptibility and magnetization measurements suggest a non-magnetic ground state with a spin gap.^{12,13} The magnitude of the gap was roughly estimated as 88 K $\sim$ 100 K (7.6 meV $\sim$ 8.6 meV). In this letter we report the first observation of the magnetic excitation in the prototype of artificial O₂ magnet realized in CPL-1 by using inelastic neutron scattering technique.

*E-mail: tmasuda@yokohama-cu.ac.jp

Neutron scattering experiment was performed using PONTA spectrometer installed in 5G beamline in JRR-3M reactor in Japan Atomic Energy Agency. A series of scans were collected by changing incident neutron energy for fixed monitor counts in a low-efficiency detector between pyrolytic graphite (PG (002)) monochromator and sample. 80' soller collimator was used between monochromator and sample. Radial collimator was installed between sample and PG horizontally focused analyzer. The energy of the final beam is fixed at 14.7 meV. PG filter was placed after sample to eliminate higher harmonics. Projected full-width at half-maximum energy resolution of this configuration at elastic position is 0.96 meV.

Schematic view of O₂ induction apparatus is shown in Fig. 2. ORANGE type cryostat is used to achieve $T = 2.0$ K. 12 g of powder sample was prepared by the previously reported method.¹¹ The sample is packed in Al cylindrical can (20 mm in diameter and 67 mm in length) which can be attached to O₂ induction probe designed for the cryostat. VCR fitting with filter gasket (Swagelok Co. Ltd.) is used for the connection to stainless made O₂ induction tube. Spacer with the height of 1cm is put in the bottom of the Al can for the reservoir of extra bulk O₂. The adsorbed water molecules in the microporous channel are eliminated by heating the sample up to 400 K in reduced pressure.

Since it is difficult to synthesize the deuterated CPL-1 we use protonated sample. To measure background from the host CPL-1 including large incoherent scattering of hydrogen atoms we performed precedent scans in the non-adsorbed CPL-1 for all scans. Afterwards the measurements for the O₂ adsorbed CPL-1 were performed. O₂ adsorption is processed by warming up the sample and by keeping the temperature at 95 K for an hour with O₂ pressure of 80 kPa.

Typical constant wave number (Q) scans of O₂ adsorbed and non-adsorbed CPL-1 are shown in Fig. 3 (a). The contribution of the adsorbed oxygen is detected as the enhanced intensity at the energy transfer ($\hbar\omega$) of about 7.8, 10.6 and 13.7 meV. We assume that the intensity in O₂ adsorbed sample is, as zeroth approximation, simple sum of the excitation from the adsorbed O₂ and the background from the host compound. Then the subtracted excitation of the adsorbed oxygen is shown in Fig. 3 (b). Solid curves are the fit to the data by triple Gaussian functions. Among the observed three peaks the peak at $\hbar\omega = 7.8$ meV shows typical behaviours of the excitation of a magnetic cluster: the peak energy does not change with Q and the peak intensity decreases with the increase of Q . In addition the peak width is within resolution limit as is indicated by shaded area. On the other hand the intensity of the peaks at $\hbar\omega = 10.6$ and 13.7 meV is almost Q independent. These peaks can be ruled out from the magnetic origin since a magnetic neutron cross section is reduced at high Q due to magnetic form factor.¹⁴ For some unknown reasons the subtracted intensity has negative values at $6\text{meV} \lesssim \hbar\omega \lesssim 10\text{meV}$ and we presumed negative background for the Gaussian fittings. Probably O₂ adsorption suppresses the incoherent scattering of hydrogen in host compound. The en-

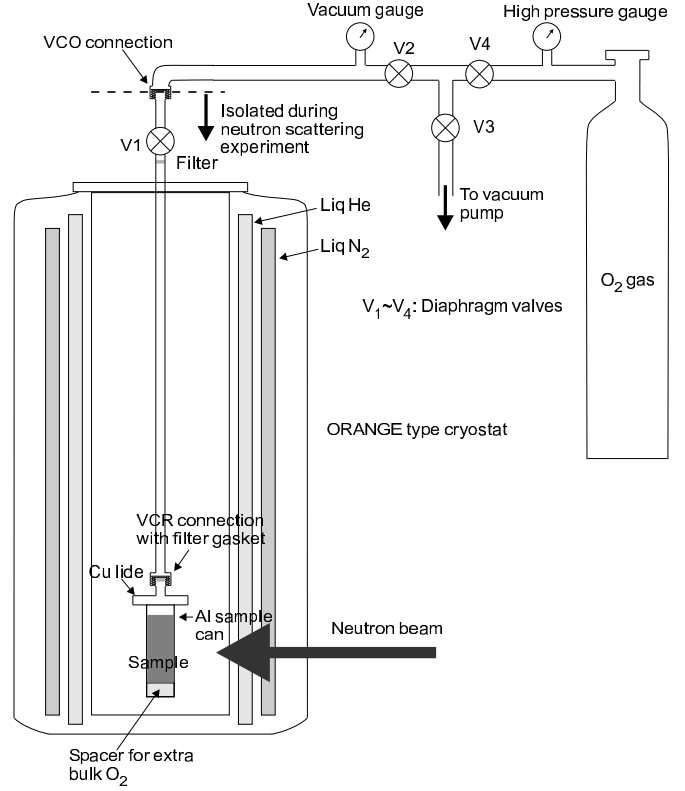


Fig. 2. Schematic view of O₂ induction apparatus.

ergy scans after the negative background subtraction are shown in Fig. 3 (c). The characteristic behaviour of the magnetic cluster is observed more clearly. Q dependence of neutron cross section at $\hbar\omega = 7.8$ meV is shown in Fig. 4. Filled circles are the net magnetic excitation of adsorbed O₂ obtained by similar data analysis in Fig. 3(c). Open circles are the scaled intensity of constant Q scans obtained in Fig. 3(c).

The most probable spin model for the magnetic cluster is Heisenberg $S = 1$ spin dimers from crystallographic consideration.¹² The effective spin Hamiltonian is described by $H = -2JS_1 \cdot S_2$. The calculated eigenenergies are $E(S) = -J(S(S+1) - 3/2)$ where S is the magnitude of the total spin operator $\mathbf{S} = \mathbf{S}_1 + \mathbf{S}_2$ ($S = 0, 1, 2$). Each energy level is $2S+1$ - fold degenerated and the energy levels satisfy Lande-interval rule. The magnetic excitation at low temperature is dominated by the transition between non-magnetic singlet ground state and $S = 1$ triplet state. The neutron cross section for the magnetic scattering is obtained¹⁵

$$\frac{d^2\rho}{d\Omega d\omega} \propto p_1(T)F^2(Q) \left(1 - \frac{\sin(QR)}{QR}\right) \delta(\hbar\omega + 2J). \quad (1)$$

Here $p_1(T)$ is a temperature factor that is proportional to the thermal population of singlet ground state: $p_1(T) = 1/(1 + 3\exp(2J/k_B T) + 5\exp(6J/k_B T))$. $F(Q)$ is magnetic form factor of oxygen molecule, Q is a scattering wave number and R is intradimer distance between oxygen molecules. For the calculation of $F(Q)$ the density of atomic $P\pm$ orbitals is assumed for the spin density of an O₂ molecule.¹⁶ Then it is obtained that $F(Q) = \int_0^\infty dr \int_0^\pi d\theta r^4 \sin^3 \theta e^{-2br^2} [\cosh(2brR_0 \cos \theta) -$

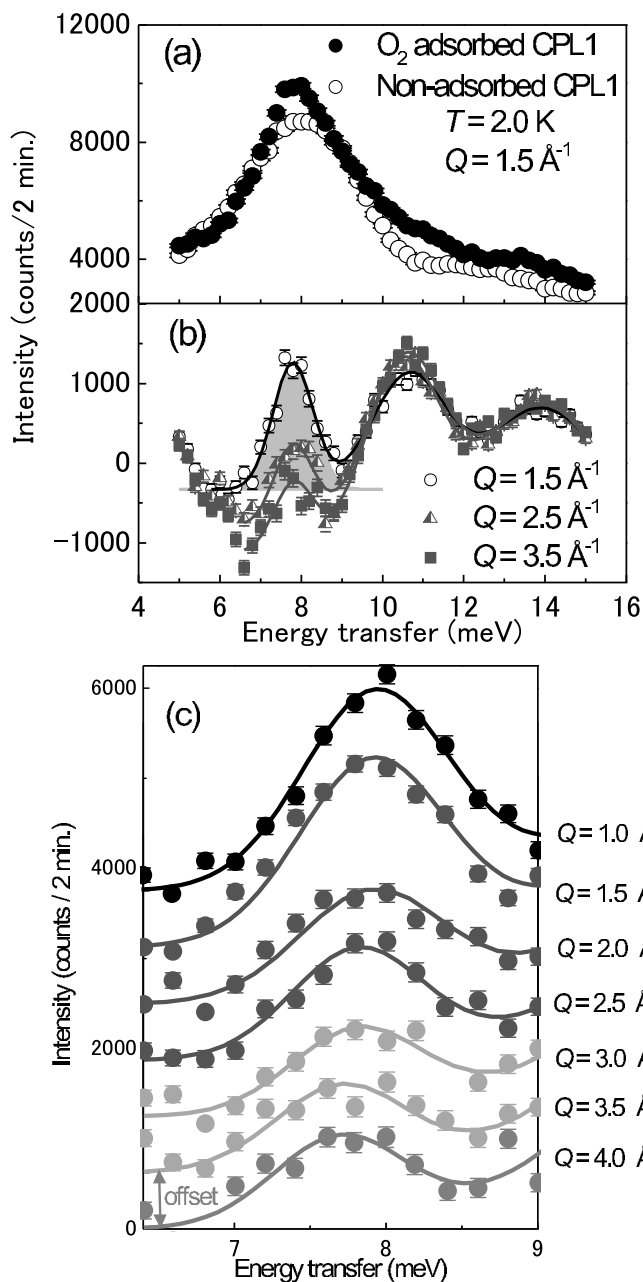


Fig. 3. Excitations of O_2 based magnet from inelastic neutron scattering measurements at $T = 2.0 \text{ K}$. (a) Constant Q scans at $Q = 1.5 \text{ \AA}^{-1}$ in O_2 adsorbed CPL-1 (filled circles) and non-adsorbed CPL-1 (open circles). (b) The subtracted intensity. Shaded area is the experimental resolution. (c) Net magnetic excitations in narrow energy range at various Q 's (offset for clarity).

$1]e^{iQr \cos(\theta-\beta)}$. Here $R_0 = 1.21 \text{ \AA}$ and $b = 4.1 \text{ \AA}^{-2}$.¹⁷ R_0 is the internuclear distance, b is a fitting parameter, and β is the angle between molecular axis and scattering vector Q . $F(Q)$ is numerically obtained by powder average $F(Q) = \int F(Q)d\Omega$.

The Q independent magnetic excitation at 7.8 meV in Fig. 3(c) is consistent with eq. (1) with $2J = -7.8 \text{ meV}$. Characteristic feature of the dimers neutron cross section is identified in constant energy scan at $\hbar\omega = 7.8 \text{ meV}$ in Fig. 4. Enhanced peak structure at $Q \sim 1.3 \text{ \AA}^{-1}$ and drastic suppression of the intensity with the increase of Q are perfectly reproduced by the calculation based on

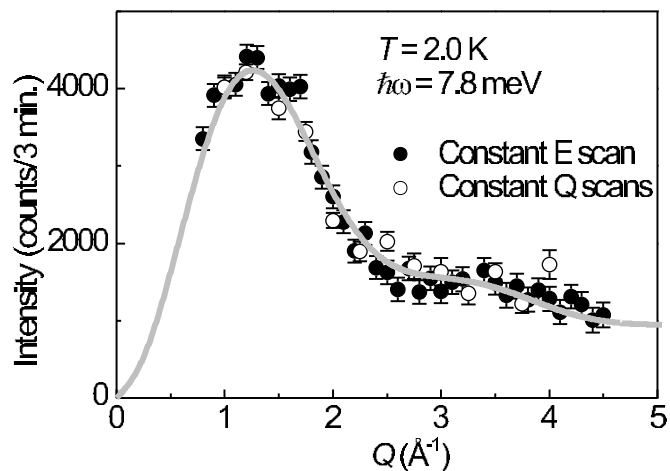


Fig. 4. Wave number dependence of the neutron cross section of the adsorbed magnetic O_2 . Symbols are the subtracted data and solid curve is the calculation of $S = 1$ spin dimer model in eq. (1) in the text.

$S = 1$ spin dimer model with $R = 3.1 \text{ \AA}$. The value of R is reasonably consistent with intermolecular distance of $R = 3.28 \text{ \AA}$ obtained by synchrotron x-ray diffraction.¹² These facts mean that magnetic excitation at $T = 2.0 \text{ K}$ is explained by the adsorbed O_2 dimers. Furthermore, the energy scale is consistent with the spin gap estimated by bulk measurements $7.6 \sim 8.6 \text{ meV}$.^{12, 13}

Constant Q scans at various temperatures is shown in Fig. 5(a). The magnetic peak at $\hbar\omega = 7.8 \text{ meV}$ is suppressed with the temperature and almost disappears at $T \gtrsim 50 \text{ K}$. As is shown in Fig. 5(b) the peak intensity goes down more rapidly than the temperature factor $p_1(T)$ shown by the solid curve. The data at $T \lesssim 40 \text{ K}$ is rather consistent with two level system with singlet ground and octet excited states described by an empirical formula $p_1'(T) = 1/(1 + 8 \exp(2J/k_B T))$.

Since the framework of O_2 molecules formed by van der Waals interaction is flexible, a magnetoelastic effect can be enhanced enough to affect the energy spectrum of the effective spin model. The calculation of the intermolecular potential of O_2 dimer showed that the energy level, particularly in high energy range, depends both on spin state and geometrical configuration.¹⁸ The ground state is $S = 0$ singlet with H configuration in Fig. 5 (c) and the first excited state is $S = 1$ triplet with the same H configuration. However, the second excited state is $S = 2$ quintet with X configuration and the energy interval from the first excited state is roughly $-2J$. This value is two times smaller than that by Lande-interval rule of the spin dimer model. These calculations indicate that the effective spin Hamiltonian works only for the low energy excitation and the inclusion of van der Waals potential is essential to the higher energy excitations. For the understanding in quantitative level the consideration of specified potential including the interaction between O_2 and CPL-1 is required in the calculation.

In summary we report the magnetic excitation of artificial O_2 magnet in microporous compound CPL-1 by using inelastic neutron scattering technique. While the neutron cross section at low temperature is completely

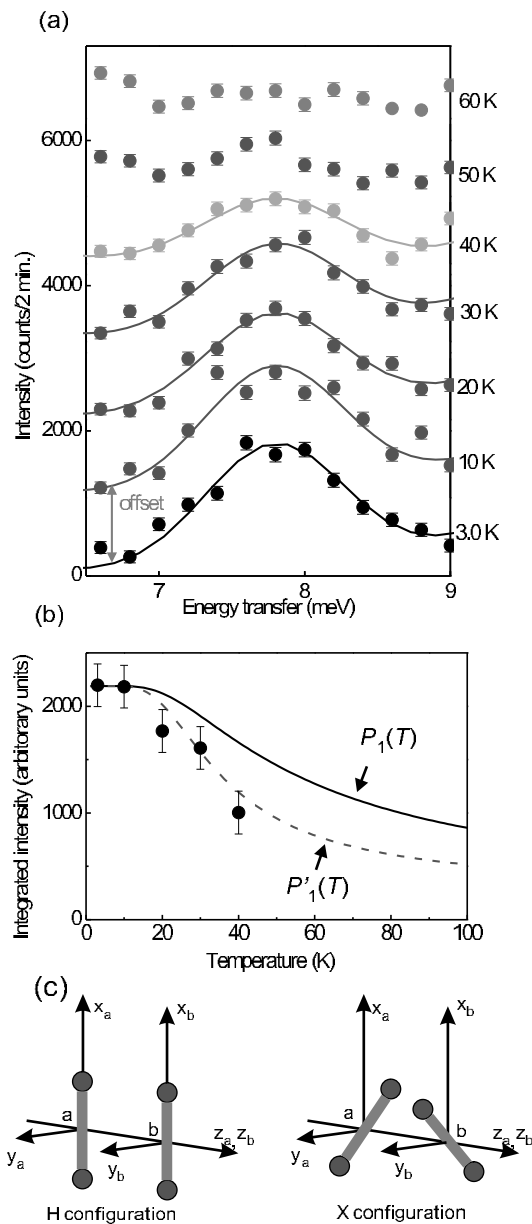


Fig. 5. Temperature dependence of the magnetic excitation. (a) Constant wave-vector scan at $Q = 1.5 \text{ \AA}^{-1}$ at various temperatures (offset for clarity). Solid curves are guide for the eyes. (b) Temperature dependence of the integrated intensity. Solid and dashed curves are temperature factors described in the text. (c) O_2 dimer in H configuration (left) and X configuration (right).

explained by existent spin model, the temperature dependence shows anomalous behaviour due to enhanced magnetoelastic effect of the adsorbed O_2 molecules. Our study demonstrates that the conventional dynamical probe for physics study, inelastic neutron scattering technique, is powerful tool for an O_2 based magnet in recent developing chemistry area.

This work was partly supported by Yamada Science Foundation, Asahi glass foundation, the Strategic Research Project (No. 19042) of Yokohama City University and Grant-in-Aid for Scientific Research (No.s 19740215 and 19052004) of Ministry of Education, Culture, Sports, Science and Technology of Japan.

- 1) C. Uyeda, K. Sugiyama, and M. Date: J. Phys. Soc. Jpn. **54** (1985) 1107.
- 2) S. Desgreniers, Y. K. Vohra, and A. L. Ruoff: J. Phys. Chem. **94** (1990) 1117.
- 3) K. Shimizu, K. Suhara, M. Ikumo, M. Eremets, and K. Ameya: Nature **393** (1998) 767.
- 4) Y. Freiman and H. Jodl: Physics Reports **401** (2004) 1.
- 5) I. Goncharenko, O. Makarova, and L. Ulivi: Phys. Rev. Lett. **93** (2004) 055502.
- 6) J. P. McTague and M. Nielsen: Phys. Rev. Lett. **37** (1976) 596.
- 7) Y. Murakami and H. Suematsu: Phys. Rev. B **54** (1996) 4154.
- 8) S. Kitagawa, R. Kitaura, and S. Noro: Angew. Chem. Int. Ed. **43** (2004) 2334.
- 9) W. Mori, T. Kobayashi, J. Kurobe, K. Amaya, Y. Narumi, T. Kumada, K. Kindo, H. Katori, T. Goto, N. Miura, S. Takamizawa, H. Nakayama, and K. Yamaguchi: Mol. Cryst. Liq. Cryst. **306** (1997) 1.
- 10) S. Takamizawa, E. Nakata, and T. Saito: Angew. Chem. Int. Ed. **43** (2004) 1368.
- 11) M. Kondo, T. Okubo, A. Asami, S. Noro, T. Yoshitomi, S. Kitagawa, T. Ishii, H. Matsuzaka, and K. Seki: Angew. Chem. Int. Ed. **38** (1999) 140.
- 12) R. Kitaura, S. Kitagawa, Y. Kubota, T. C. Kobayashi, K. Kindo, Y. Mita, A. Matsuo, M. Kobayashi, H.-C. Chang, T. C. Ozawa, M. Suzuki, M. Sakata, and M. Takata: Science **298** (2002) 2358.
- 13) T. Kobayashi, A. Matsuo, M. Suzuki, K. Kindo, R. Kitaura, R. Matsuda, and S. Kitagawa: Prog. Theor. Phys. Suppl. **159** (2005) 271.
- 14) S. Lovesey: *Theory of Neutron Scattering from Condensed Matter vol.2*, Oxford university press, (1984).
- 15) A. Furrer and H. Gudel: J. Magn. Magn. Mater. **14** (1979) 256.
- 16) W. Kleiner: Phys. Rev. **97** (55) 411.
- 17) P. Stephens: Phys. Rev. B **31** (1985) 4491.
- 18) B. Bussery and P. Wormer: J. Chem. Phys. **99** (1993) 1230.